

# Effect of Tool Rotational Speed on Tensile and Impact Strength of Friction Stir Welded joints of Aluminum 6063 Alloy

<sup>1</sup>Inderjeet Singh, <sup>2</sup>Harjot Singh, <sup>3</sup>Ankit Chopra

<sup>1,2</sup>Dept. of Mechanical Engineering, Punjab Technical University, Jalandhar, Punjab, India

<sup>3</sup>Chandigarh Engineering College, Landran, Punjab, India

## Abstract

Aluminum 6063 as a light weight structural material with high specific strength, good damping capability and machine ability, is one of the most attractive material in applications of transportation and mobile electronics for effectively reducing weight. The selected material was welded with Friction Stir Welding using combination of different parameters i.e. tool rotational speed (1000 rpm, 1200 rpm, 1400 rpm, 1600 rpm and 1800 rpm) and constant welding speed of 25 mm/min. A cylindrical left hand threaded tool with 20 mm tool shoulder diameter and 7 mm pin diameter was employed for welding. The effect of tool rotational speed was examined on the mechanical properties. It was observed that excessive heat generation and insufficient flow of plasticized material at higher values of tool rotational speed, leading to formation of defects which ultimately results in failure of weld joints between Stir Zone and Thermo mechanically affected Zone.

## Keywords

Friction Stir Welding, Stir Zone, Ultimate Tensile Strength, Advancing Side (AS) Heat Affected Zone (HAZ)

## I. Introduction

Friction Stir Welding (FSW) is a solid state welding process first discovered and patented by the Welding Institute of Cambridge U.K. in 1991 by Wayne Thomas et al. and has been since then the subject of a great deal of interest. FSW friction generated by a rotating cylindrical tool to heat and plasticize metal on either side of a joint for obtaining a solid and functional weld. Friction generated heat is more effective at reorganizing the microstructure of metals and metal alloys than other forms of fusion welding. Friction Stir process uses a rotating, non-consumable weld tool that plunges into the base material and moves forward. Friction heat caused by the rotating pin creates a plasticized tubular shaft around the pin [2]. Pressure provided by the weld tool forces the plasticized material to back of the pin. Aluminum alloy is difficult to weld by traditional methods, due to high thermal conductivity, resulting in defects like porosity, cracks etc.

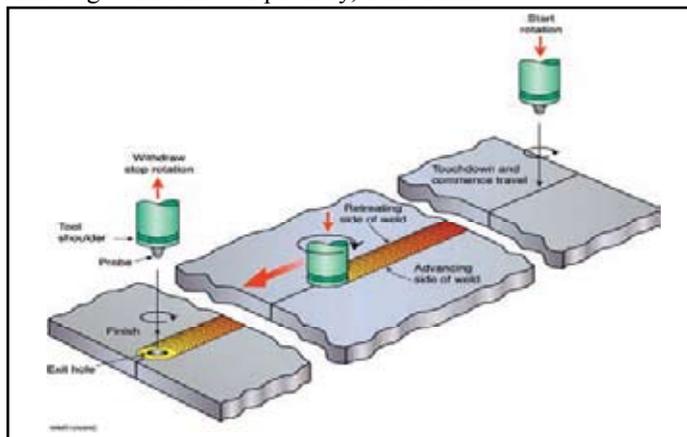


Fig. 1: Friction Stir Welding Operation

Hence FSW is being increasingly used. The process is especially well suited to butt and lap joint in aluminum since aluminium is difficult to weld by arc welding. The present work is aimed to the evaluation of tool rotational speed effect on mechanical properties of AA6063 welded plates with thickness 5 mm, obtained by different Friction stir welding parameters.

## II. Experimental Procedure

The material under investigation was a 6063 aluminium alloy under the form of rolled plates of 5 mm thickness. Ten plates of size 152 mm x 77 mm were prepared to obtain five Friction Stir Welded joints with different welding parameters. Plates were welded perpendicularly to the rolling direction. The employed tool rotating speeds of the cylindrical threaded tool was 1000 rpm, 1200 rpm, 1400 rpm, 1600 rpm and 1800 rpm with constant welding speed of 25 mm/min. A 20 mm tool shoulder diameter with pin diameter of 7 mm and 4.8 mm long was used. Tool profile used in this study was shown in fig. 2.

A cold-work tool High carbon, high chromium oil hardened type steel tool that comprises of outstanding high temperature strength, high temperature toughness, high temperature wear resistance and good machine ability is selected for present work. This tool steel selection was also motivated by its cost and availability [11].



Fig. 2: Welding Tool Profile

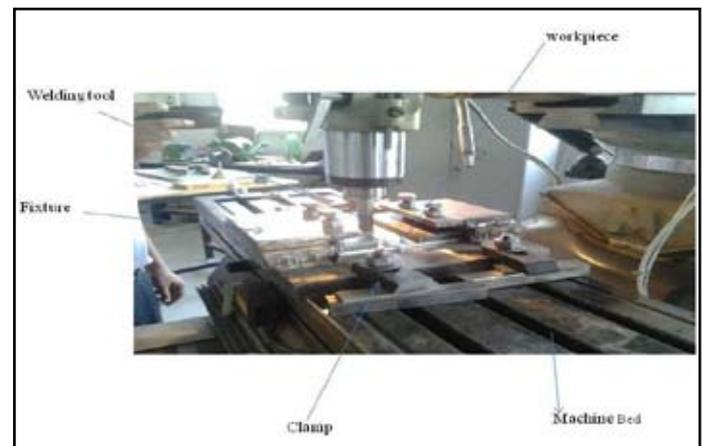


Fig. 3: Work Piece and Fixture Set Up

For Friction stir welding process cut edges are finished with milling operation so that interfaces can be properly matched. The machine used for the production of the joints was semi automated vertical milling machine. Fixture was first fixed on the machine bed with help of clamps and then plates were held in the fixture properly for Friction Stir Welding as shown in fig. 3.

Ten aluminum plates of size 152 mm x 77 mm were prepared to obtain five Friction Stir Welded joints at selected tool rotational speeds. Specimens for the tensile strength analysis cut perpendicular to the weld line as shown in the fig. 4.

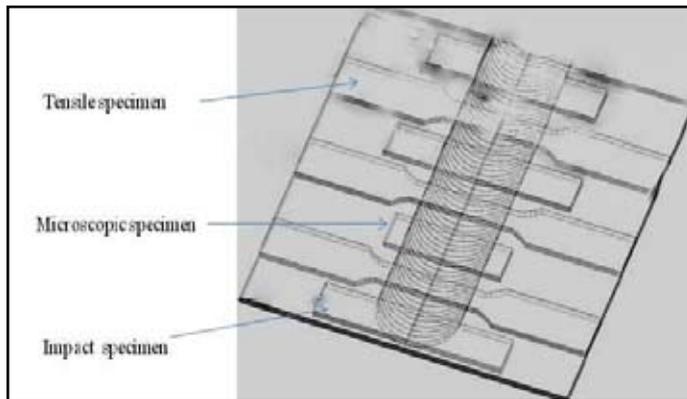


Fig. 4: Tested Specimen Cutting Scheme

Tensile test specimens were prepared from each weld in accordance with ASTM specifications, E-8M-08, having specimen of 50 mm gauge length and 12.5 mm width [1]. Tensile test was carried out at a constant speed of 2 mm/min at 16 kN load. The load was applied until the necking was there and specimen failed, 20 specimens were prepared from welded joints and 2 specimens were prepared from base material for tensile testing. Servo Control Universal testing machine. Tensile test specimens before and after tensile testing are shown in fig. 5 and fig. 6 respectively.



Fig. 5: Specimens Before Testing



Fig. 6: Specimens After Testing

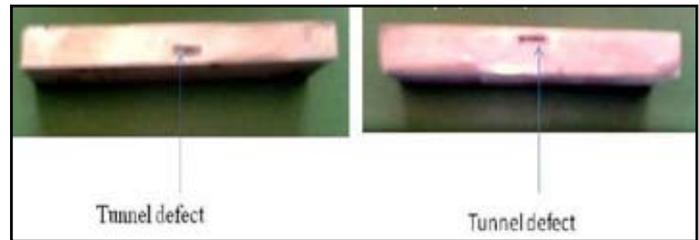


Fig.7: Tunnel Defects

Visual inspection was performed on all welded samples in order to verify the presence of macroscopic external defects such as surface irregularities, excessive flash, lack of penetration, voids and surface open tunnel defects [8]. The excessive flashes and tunnel defects as shown in fig. 7 were absorbed at higher rotational speed of 1800 rpm due to sufficient stirring and improper interaction of tool shoulder and work piece. It was observed in the visual inspection of the welded specimens that, specimens welded with tool rotational speed 1200 rpm, welding speed 25 mm/min with tool shoulder diameter of 20 mm shows better surface texture as compare to other joints welded at other selected tool rotational speeds. This shows that at 1200 rpm tool rotational speed, 25 mm/min welding speed along with 20 mm tool shoulder diameter was sufficient to join the plates with better surface textures.

### III. Results and Discussion

FSW has become a very effective tool in solving the joining problems of profiled sheets with material continuity, without using different joining methods; particularly in case of aerospace industry, where high ductility and tensile strength are required. In the present work, different FSW butt welds of Aluminium 6063 sheets were successfully obtained by varying the processing parameters.

#### A. Tensile Characteristics

The specimens were tensile tested and transverse tensile properties such as Ultimate Tensile Strength (UTS) and percent elongation were evaluated. The four specimens were welded and numbered according to the Table 1 which was followed throughout the study. The specimen 2 exhibits high UTS of 189 N/mm<sup>2</sup>, which is having a joint efficiency of 91.6%. Majority of the specimens were fractured at location between TMAZ and SZ. This is due to the fact that the accumulation of basal slips plane (0001) having their normal parallel to the transverse direction is maximum in that location leading to minimum Schmid Factor [12].

Table 1: Tensile Test Results

Sr. no.	Rotational speed (rpm)	Welding speed (mm/min)	UTS (N/mm <sup>2</sup> )	% elongation
1	1000	25	184.5	8
2	1200	25	189	12
3	1400	25	187.6	10
4	1600	25	183.4	8
5	1800	25	174	6

UTS first increases with further increment in rotational rate of 1000 rpm to 1200 rpm due to proper heat generation and sufficient material flow from Advancing side (AS) to retreating side (RS). The UTS values at rotational speeds of 1000 rpm and 1200 rpm at constant welding speed of 25 mm/min with 20 mm tool

shoulder diameter were observed 184.5 N/mm<sup>2</sup> and 189 N/mm<sup>2</sup> respectively. A decline in UTS value was observed at higher tool rotational speeds of 1400 rpm, 1600 rpm and 1800 rpm, this is due to the fact that the higher rotational speed leads to high temperature near the threaded pin surface would result in a higher probability for the occurrence of lack of bonding near bottom surface [4]. Thus tunnel defects are observed at high tool rotational speeds due to insufficient material flow [4] from advancing side to retreating side. This is also pointed out that LHT pin tool with clockwise rotations, the plasticized material flow is not a vertical upward but it is a inclined upward from RS to AS at the trailing side as a result of clockwise rotation. The material flow continuously from bottom of the screw thread to the shoulder of rotating tool. The transported material underneath the shoulder is pushed into a downward direction to fill the cavity at bottom of joint that was already created due to inclined upward flow of material in the vicinity of threaded pin [9]. Thus tunnel defects are observed at high tool rotational speeds due to insufficient material flow [8].

### B. Effect of Tool Rotational Speed on Impact Strength

There was an insignificant effect of welding parameters on the impact strength was observed. But slight decrease in impact value was observed at higher tool rotational speed of 1600 rpm and 1800 rpm, due to formation of tunnel defects. Hence high impact strength at the rate of 3 J was obtained with 1200 rpm tool rotational speed. The reduction in impact strength in welded joint, welded with selected tool rotational speed was observed due to formation of tunnel defects.

### V. Conclusion

In this work, a study of five tool rotational speeds has been carried out. The tool rotational speed analysis has been carried out on AA 6063 alloy of 5 mm thick plates. The welding process was carried out at a constant welding speed of 25 mm/min with 20 mm tool shoulder diameter.

UTS increases with increasing tool rotational speed from 1000 rpm to 1200 rpm at constant welding speed after it started decreasing under selected parameters. In this investigation a lower value of UTS was observed at 1800 rpm due to formation of tunnel defects due to high rate of stirring action and increase in size of TMAZ and HAZ region. Most of the welded joints were fractured in a area between SZ and TMAZ towards AS because of softening point at this point. A 45° fracture angle was observed in the majority of joints. Defects were observed near the bottom surface of the SZ.

Insignificant effect of welding parameters on the impact strength was observed. But slight decrease in impact value was observed with increase in tool rotational speed, due to formation of tunnel defects.

Selected tool material i.e. High chrome high carbon steel withstands at high tool rotational speed and performs Friction Stir welding with negligible wear.

### References

- [1] Afrin, N. Chen, D. Cao, X., Jhazi, M., "Micro structure and tensile properties of Friction Stir Welded AZ31B magnesium alloy", *Material Science and Engineering*, Vol. 472, 2007, pp. 179-186, 2007.
- [2] Blignaulh, C., "Design, Development and Analysis of Friction Stir Welding process", 2002.
- [3] Cavaliere, P., Squillace, A., Campanile, G., Panella, F., "Effect of welding parameters on mechanical and microstructure

properties of AA6056 joints produced by friction stir welding", *J. Mater. Process. Technol.* 180, pp. 263–270, 2006.

- [4] Chowdhary, S.M. Bhole, D., Cao, X., "Tensile properties of friction stir welded magnesium alloy, effect of pin thread orientation and weld pitch", *Material science and Engineering*, Vol. A527, 2010, pp. 6064-6067, 2010.
- [5] Ericsson, M., Sandstrom, R., "Influence of welding speed on the fatigue of friction stir welds, and comparison with MIG and TIG", *Int. J. Fatigue* 25, pp. 1379–1387, 2003.
- [6] Mishra, R.S., Ma, Z.Y., "Friction stir welding and processing." *Material Science and Engineering R* 50, 1–78, 2005.
- [7] Canalier, P., Squillace, A., Panella, F., "Effect of welding parameters on mechanical and microstructural properties of AA6082 joints produced by friction stir welding", *Journal of Material Science and Technology*, pp. 364-372, 2007.
- [8] Rhodes, C.G., Mahoney, M.W., Bingel, W.H., "Effects of friction stir welding on microstructure of 7075 aluminium", *Scripta Mater.* 36, pp. 69–75, 1997.
- [9] Simoncin, M., Forcellese, A., "Effect of welding parameters and tool configuration on micro-and macro-mechanical properties of similar and dissimilar FSWed joints in AA5754 and AZ31 thin sheets", *Materials and Design*, Vol. 41, 2012, pp. 56-60, 2012.
- [10] Singh, G. Singh, K., Singh, J., "Effect of process parameters on microstructure and mechanical properties in friction stir welding of aluminum alloy", *Indian institute of metals*, 2011.
- [11] Scialpi, A. De Fllippis, L.A.C., Cavaliere, P., "Influence of shoulder geometry on microstructure and mechanical properties of Friction Stir Welded 6082 Aluminium alloy", *Material and Design*. Vol. 28, pp. 1124-1129, 2007.
- [12] Woo, W. Choo, H. Brown, D.W. Liaw, P.K., Fing, H., "Texture variations and its influence on tensile behavior of a Friction Stir Processed magnesium alloy", *Scripta Material*, Vol. 54, 2006, pp. 1859-1864, 2006.



Er. Inderjeet Singh is Assistant Professor at Chandigarh Engineering College, Landran, Mohali.



Er. Harjot Singh is Assistant Professor at Chandigarh Engineering College, Landran, Mohali.